

This item is the archived peer-reviewed author-version of:

The design of magneto-plasmonic nanostructures formed by magnetic Prussian Blue-type nanocrystals decorated with Au nanoparticles

Reference:

Sanchis-Gual Roger, Susic Isidora, Torres-Cavanillas Ramón, Arenas Esteban Daniel, Bals Sara, Mallah Talal, Coronado-Puchau Marc, Coronado Eugenio.-
The design of magneto-plasmonic nanostructures formed by magnetic Prussian Blue-type nanocrystals decorated with Au nanoparticles
ChemComm / Royal Society of Chemistry [London] - ISSN 1359-7345 - 57:15(2021), p. 1903-1906
Full text (Publisher's DOI): <https://doi.org/10.1039/D0CC08034A>
To cite this reference: <https://hdl.handle.net/10067/1765420151162165141>

COMMUNICATION

Design of magneto-plasmonic nanostructures formed by magnetic Prussian Blue-type nanocrystals decorated with Au nanoparticles

Received 00th January 20xx,
Accepted 00th January 20xx

Roger Sanchis-Gual,^a Isidora Susic,^a Ramón Torres-Cavanillas,^a Daniel Arenas-Esteban,^b Sara Bals,^b Talal Mallah,^c Marc Coronado-Puchau,^{*a} Eugenio Coronado^{*a}

DOI: 10.1039/x0xx00000x

We have developed a general protocol for the preparation of hybrid nanostructures formed by nanoparticles (NPs) of molecule-based magnets based on Prussian Blue Analogues (PBAs) decorated with plasmonic Au NPs of different shapes. By adjusting the pH, Au NPs can be attached preferentially along the edges of the PBA or randomly on the surface. The protocol allows tuning the plasmonic properties of the hybrids in the whole visible spectrum.

Magneto-plasmonic nanoparticles (NPs) are one of the emerging multifunctional materials in the fields of physics¹ and nanomedicine.² Still, most of the work in this topic have been focused on the design of core@shell NPs formed by an inorganic magnetic core (typically a metal oxide) and a gold plasmonic shell. An interesting alternative is replacing the magnetic inorganic core by a molecule-based magnet instead of a pure inorganic one since the former can provide some advantages in terms of chemical versatility, tunability of the properties and optical transparency.³ In spite of these features, this possibility has remained so far almost unexplored.

Thus, the only example of hybrid molecular-plasmonic nanostructure is that made of a gold core and a shell of Prussian Blue (Au@PB), where PB refers to the so-called Prussian Blue, a bimetallic cyanide-bridged cubic network formulated as $\text{Fe}^{\text{III}}_4[\text{Fe}^{\text{II}}(\text{CN})_6]_3$ (in short FeFe).⁴ Note that PB is the first member of an extensive family of coordination polymers of general formula $\text{A}_x\text{M}_y[\text{M}'(\text{CN})_6]_z \cdot n\text{H}_2\text{O}$ (A = alkali cation, M and M' = transition metal ions) known as Prussian Blue Analogues (PBAs), which have aroused strong interest in molecular magnetism,^{5,6} materials science^{7–9} and medicine.¹⁰ In magnetism this family is very appealing since it provides unique examples of high- T_c magnets¹¹ and photomagnets.¹² However, the chemical approach required to prepare the core@shell (Au@PB) nanostructures is quite limited since it is restricted to use as shell PB (FeFe), or to the reduced form of the NiFe PBA derivative, only.^{13–16} These two derivatives are weakly magnetic since they undergo long-range magnetic ordering at low temperatures only ($T_c = 5.6$ and 2 K, respectively). Hence, they are not useful to investigate the enhanced

magneto-optical (MO) properties that may arise in these systems as a result of the coupling of the magnetic and the plasmonic components.^{17,18} To overcome this limitation, other PBAs exhibiting higher T_c values need to be grown directly on the Au core. Nevertheless, this still requires the insertion of a NiFe layer in between the Au and the PBA magnetic shell, which strongly limits the interaction between the magnetic layer and the plasmonic core and prevents the appearance of noticeable magneto-plasmonic effects.¹⁹ A second limitation of this procedure is that it is restricted to spherical Au NPs because anisotropic shapes (such as nanorods (NRs) or nanostars (NSs)) are too reactive towards cyanide. Still, these limitations have not been too problematic for using this kind of nanostructures in biomedicine (dual function NPs for imaging, photothermal therapy, or biosensing)^{20,21} and electrocatalysis.^{22,23}

Hereby, we propose a simple and versatile approach that allows synthesizing hybrid Au-PBA nanostructures formed by a PBA cubic NP surrounded by Au NPs of different shapes and connected to the PBA surface through a bridging molecule. Thanks to the different plasmonic NPs, the developed protocol allows tuning the plasmon band position in the whole range of the visible spectrum.

The synthetic strategy is illustrated in Figure 1 using NPs of the NiCr magnetic PBA derivative that may have a T_c as large as 90 K in its bulk form.²⁴ The PBA-NPs are negatively charged and are stable in water in the absence of any coating agent. They are obtained by mixing the corresponding precursors (equimolar 10^{-3} M aqueous solutions of $\text{K}_3[\text{Cr}(\text{CN})_6]$ and $\text{NiCl}_2 \cdot (\text{H}_2\text{O})_6$) under vigorous stirring at room temperature. Cubic shape NPs of $\text{K}_{0.07}\text{Ni}[\text{Cr}(\text{CN})_6]_{0.69}$ were obtained with a mean size of 140 ± 40 nm (Figure S2) and a negative ζ -potential value of -37 ± 11 mV. The first step consists of exchanging, in aqueous solution the citrate molecules that coat the Au NPs, by the heteroditopic thiol-polyethyleneglycol-amine (HS-PEG-NH₂) ligand. In a second step, the as-obtained Au NPs are anchored to the PBA NPs suspended in water. Such a decoration takes place due to: i) the strong affinity of the thiol group to the metal particle surface²⁵ and ii) the strong interaction between the amine group and the negatively charged PBA NPs. It is worth noting that the formation of the final hybrid nano-objects is not possible using the citrate-stabilized Au NPs due to the

^a Instituto de Ciencia Molecular, Universitat de València, Catedrático José Beltrán 2, 46980, Paterna, Spain

^b Electron Microscopy for Materials Science (EMAT) and NANOLab Center of Excellence, University of Antwerp, Groenenborgerlaan 171, 2020 Antwerp, Belgium

^c Institut de Chimie Moléculaire et des Matériaux d'Orsay, Université Paris-Saclay, CNRS, 91405 Orsay Cedex, France

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

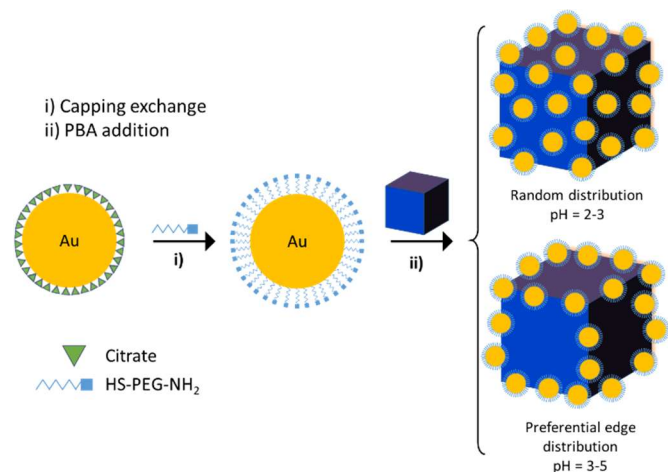


Figure 1. Schematic illustration for the preparation of a heterostructure formed by Au nanospheres decorating PBA NPs. First step involves a capping substitution and the second step the attachment of the Au onto the PBA surface. Two different Au decoration can be achieved by adjusting the pH solution: a random and a preferential distribution along the edges.

electrostatic repulsion between the two systems because they are both negatively charged (see Figure S7). That is why the first step requires a ligand exchange of the starting citrate-stabilized Au NPs of 12.4 ± 1.0 nm (see Figure S3)²⁶ with HS-PEG-NH₂. This ligand exchange was monitored by ζ -potential (see Table S1) and by attenuated total reflectance Fourier-transform infrared (ATR-FTIR, Figure S16). The ζ -potential varies from a negative value, corresponding to the citrate capping, to a positive value, related to the HS-PEG-NH₂. In addition, the appearance in the ATR-FTIR measurements of bands corresponding to C-H and C-O-C vibration modes of the PEG molecule and the decrease of the intensity of the citrate bands indicate a major substitution of citrate by the heteroditopic ligand.

In a further step, the solution of Au NPs stabilized with HS-PEG-NH₂ was adjusted at pH between 2 and 4 in order to protonate the dangling amine group (ζ -potential values vary from 9 ± 6 mV to > 20 mV). Mixing this solution with PBA NPs resulted in the decoration of the PBA NPs by the Au NPs. pH plays an important role in the whole process because at low pH (below 2) the Au NPs tend to aggregate (strong ionic force), while at high pH (above 5) a poor decoration of the PBA NPs is observed (weak electrostatic interaction because the weak positively charged Au NPs) (Figure S1). Hence, to optimize the decoration, the pH value was kept in the range of 2-5.

When the pH is in the 2-3 range, a random decoration of the PBA-NPs by Au is obtained, as demonstrated by Transmission Electron Microscopy (TEM) imaging. (Figure 2a and S8). An increase of the pH value (3-4) leads to a preferential binding of the Au NPs along the edges of the PBA cube (Figure 2b and S8). TEM images of the preferential edge decoration taken at different incidence angles are shown in Figure S9. In addition to this, 3D imaging by tomography of both heterostructures was performed to visualize these complex morphologies. The 3D images confirm the preferential pH-dependent decoration of the edges of the PBA-NPs by the Au ones (see Figure S10 and videos of the 3D reconstructions in the Supporting Information). Energy-dispersive X-ray spectroscopy mapping (Figure S11) confirms the presence of Cr and Ni at the center of the NP and Au at its edges. The selective decoration of the PBA-NPs edges

at higher pH is due to the larger negative charge density on (and near) the NPs edges than on their faces. Indeed, on the particles' surface, each $\text{Cr}(\text{CN})_6^{3-}$ species is surrounded by 5 Ni^{2+} (four belonging to the surface and one inside the NP), while on the edges each hexacyanometalate is surrounded by only four Ni^{2+} (two belonging to the surface and two to the particles' edge). At large pH, the positive charge density of the Au NPs is weaker, therefore, privileging electrostatic interaction with the PBA-NPs edges where the negative charge density is larger. This effect is enhanced because of the possible presence of a larger amount of defects in the vicinity of the NPs edges than on their faces.

An optimum decoration of the PBA-NPs can be achieved by tuning the ratio (Au:PBA) of the two components for the two pH ranges. For the low pH range, we carried the experiments with Au:PBA molar ratio in the range 0.31 to 0.50. In this range, the higher the ratio is, the higher the decoration is (Figure S12). For high pH range (edge distribution), we investigated three different ratios, namely 0.28, 0.41 and 1.12. TEM imaging seems to indicate that the best results are obtained with the molar ratio of 0.41 (Figure S13). In order to assess the efficiency of the interaction between the two types of NPs, we determined the molar ratio of two thoroughly washed powder samples obtained with Au:PBA = 0.51 (low pH range) and 0.41 (high pH range) using inductively coupled plasma (ICP) measurements. Values of the Au:PBA ratio of 0.43 and 0.26 were obtained for the former and latter cases respectively, allowing the determination of the optimum ratio for the two pH ranges.

We have presented a new synthetic approach that allows an optimum selective decoration (random vs preferential) of PBA NPs with Au NPs. Let us now discuss the plasmonic and magnetic properties of these hybrid nanostructures.

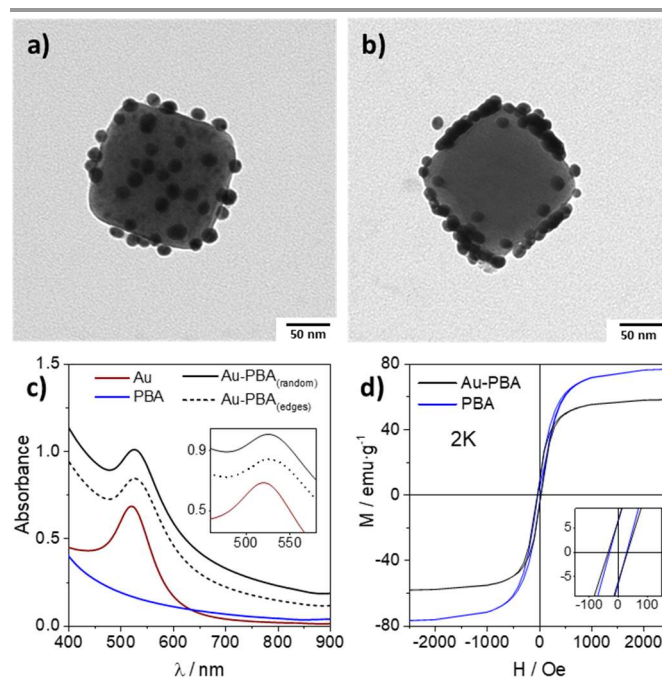


Figure 2. TEM images obtained for a single NP of the heterostructure of Au NPs with (a) random and (b) preferential edge decoration onto NiCr PBA. c) Spectra of Au NPs and Au-PBA heterostructures in the visible region. Inset: magnified image of the plasmon bands. (d) Hysteresis loop at 2K of PBA and Au-PBA.

The optical properties of Au NPs arise from the Localized Surface Plasmon Resonance (LSPR). Hence, the plasmon band is expected to be sensitive to the interaction between Au and PBA NPs. In Figure 2c, we observe that the UV-vis absorption spectrum is dominated by the plasmon band. For the functionalized Au-PEG NPs, the maximum of this band is located at 520 nm and shifts to 526 nm when Au-PEG is attached to the PBA-NPs, independently on the type of decoration. The plasmon band shift is related to the change of the dielectric properties and, in particular, to the local refractive index at the surface of the plasmonic NPs.^{27,28} It is worth noting that no shift is observed in the control experiment where the HS-PEG-NH₂ molecule was not used (see Figure S8). Therefore, this shift is a clear indication of the PBA NPs decoration by the functionalized Au NPs. However, we also observe a progressive decay of the absorbance of the plasmonic band after 2 hours that becomes large after 48 h (Figure S17). A decrease of intensity of the plasmonic band is usually associated with the aggregation of the colloidal suspension but may be also due to Au degradation in the present case. Indeed, cyanide dissolution of spherical Au colloids usually takes place quickly;²⁹ thus, in order to check the chemical stability of the hybrid materials, X-ray powder diffraction study was performed on the pure PBA NPs and the hybrid material after leaving the suspensions to stand 1 week in water (see Figure S18). The detection of the characteristic Au diffraction peaks (at 38.2 and 44.3 degrees), together with unaltered PBA peaks indicate that the decrease of the intensity

of the plasmonic band is due to the aggregation of the colloidal suspension with time and not to chemical degradation of the hybrid materials.

As far as the magnetic properties of the hybrid nanostructures are concerned, we observe that they are almost identical to those measured for pristine NiCr PBA NPs (Figures S19, S20 and 2d).³⁰ Thus, a ferromagnetic behaviour below 68 K and a weak hysteresis in the magnetization of *ca.* 60 Oe at 2 K is observed, in agreement with the soft character of this PBA derivative (Figure 2d). The only noticeable difference between hybrid and pristine NPs is the lower value for the saturation magnetization. This is due to the contribution of Au in the total weight of the nanostructure. In fact, if the presence of Au is corrected using the estimated amount of Au extracted from ICP measurements, such a difference disappears.

The generality of this approach is further illustrated by the fact that any plasmonic NP able to form thiol bonds with HS-PEG-NH₂ in acid conditions can be potentially used. This possibility opens the door to tune at will the plasmonic properties of the hybrid nanostructure simply by choosing the appropriate plasmonic NP. In this manner, citrate-stabilized spherical Ag NPs were used instead of Au NPs following the same experimental procedure (see Figure S4 and Table S1). The obtained results are shown in Figures 3a and 3b. The plasmon band of the Ag NPs is now located at 410 nm (to be compared with 520 for the Au-NPs) and exhibits a red-shift of *ca.* 7 nm. This shift is similar to that observed in Au NPs, as it mainly depends on the shape of the NP, being independent of the metal.³¹ Other Au NP with different shapes can also be used to decorate the NiCr PBA. Thus, we have chosen anisotropic Au NPs (NRs and NSs; see Figures S5 and S6) which exhibit an intense plasmon band located at *ca.* 800 nm and *ca.* 700 nm respectively. In these cases, the plasmon band can be tuned in a broad range, by changing the ratio length/width in the AuNRs,³² and the size of the branches and the core for the AuNSs.³³ In these two cases the optimal ratio of Au:PBA changes with respect to that of the Au spheres, being 0.55:1 and 1.25:1 for AuNRs-PBA and AuNSs-PBA, respectively. This variation can be attributed to the different contact areas obtained for the different structures.

Figure 3 shows the resulting nanostructures and plasmonic properties. As in the previous case, the synthesis was followed by UV-Vis spectra, searching for the plasmon shift as a proof of the interaction between Au and PBA NPs. In both cases, a shift in the plasmon band was noticed. Nevertheless, these shifts were more pronounced than the one observed for the Au spheres, due to the higher sensibility of these plasmons.^{27,28} Concretely, AuNRs and AuNSs hybrid nanostructures show plasmon red-shifts of *ca.* 9 nm and 22 nm, respectively.

The possibility to cover the whole visible spectrum by choosing the appropriate plasmonic NP may be very interesting for improving the magneto-plasmonic properties of these hybrids since the MO response of the magnet is enhanced when its maximum matches in energy that of the plasmon band.¹⁷ Since this synthetic strategy enables to prepare many different combinations of plasmonic NPs with PBAs, it can also be suitable for biomedical applications, where a NIR plasmon needs to be combined with an efficient PBA contrast agent.

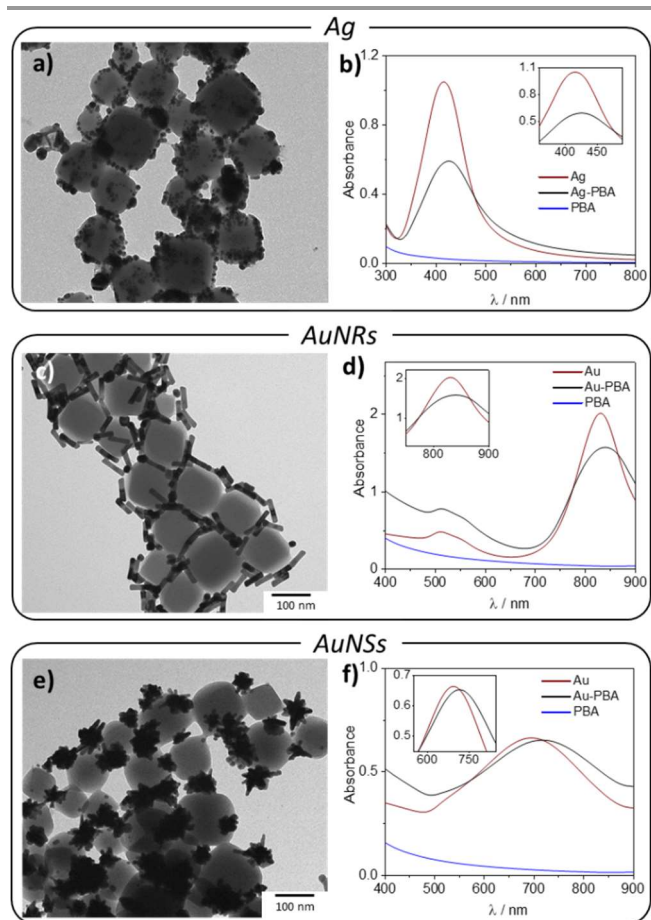


Figure 3. TEM images and UV-Vis spectra obtained for the heterostructures: Ag-PBA, AuNRs-PBA and AuNSs-PBA. The insets show the plasmon band shift.

Finally, it can be noted that this procedure can also be extended to other PBA NPs. For example, NiCr can be changed by PB (FeFe), which was obtained as NPs with a size of 110 ± 20 nm and a ζ -potential value of -34 ± 4 mV. Figures S12a and S12b show the nanostructures achieved, as well as the corresponding shift in the UV-Vis spectrum of ca. 6 nm. Therefore, following this approach it is possible to attach Au NPs in any negatively charged PB or PBA NPs without capping agent, such as NiFe, CuCr or CoFe. These nanostructures can be observed in Figure S14. Notice however that the colloidal stability of these systems is limited by the size of the PBA NPs since, if they are too small (below 25 nm), the NPs tend to aggregate (see Figure S15).

In summary, we have developed a simple and general synthetic procedure to prepare, in aqueous solution, hybrid magneto-plasmonic nanostructures formed by metallic NPs decorating negatively charged magnetic NPs based on Prussian Blue Analogues. By adjusting the pH, it is possible to control the location of the Au NPs on the PBA cubic NP. Indeed, Au can be attached randomly over the whole cubic surface or preferentially on the edges. This general methodology was first tested with spherical Au NPs and then extended in a second step to different plasmonic NPs of various shapes. It permitted tuning the plasmon band energy in a broad range of the visible spectrum, thus providing a versatile platform to investigate the enhancement of the magneto-optical properties of the hybrids thanks to their coupling with the plasmons. This aspect, fully unexplored in molecular-based magnets, will be addressed in the future combining photomagnetism with plasmonic.

The authors acknowledge funding from the EU (COST Action MOLSPIN CA15128, ERC Advanced Grant Mol-2D 788222, ERC Consolidator Grant REALNANO 815128 and Grant Agreement No. 731019 (EUSMI) under the Horizon 2020 Programme), the Spanish MCIU (Unit of Excellence "Maria de Maeztu" CEX2019-000919-M and Project MAT2017-89993-R co-financed by FEDER), the Generalitat Valenciana (Prometeo Programme PROMETEO/2017/066 and iDiFEDER/2018/061) and the Ministry of Education and Science of Russian Federation (Agreement No.14.W03.31.0001). R.S.-G. and R.T.-C. thank the Spanish MCIU for the F.P.U. and F.P.I. fellowships.

Conflicts of interest

There are no conflicts to declare.

Notes and references

- I. S. Maksymov, *Rev. Phys.*, 2016, **1**, 36–51.
- T. T. Nguyen, F. Mammeri and S. Ammar, *Nanomaterials*, 2018, **8**, 149.
- E. Coronado, *Nat. Rev. Mater.*, 2020, **5**, 87–104.
- L. Catala and T. Mallah, *Coord. Chem. Rev.*, 2017, **346**, 32–61.
- E. Coronado, M. Makarewicz, J. P. Prieto-Ruiz, H. Prima-García and F. M. Romero, *Adv. Mater.*, 2011, **23**, 4323–4326.
- S. H. Lapidus, A. G. Graham, C. M. Kareis, C. G. Hawkins, P. W. Stephens and J. S. Miller, *J. Am. Chem. Soc.*, 2019, **141**, 911–921.
- S. Ohkoshi, A. Namai and H. Tokoro, *Coord. Chem. Rev.*, 2019, **380**, 572–583.
- K. Hurlbutt, S. Wheeler, I. Capone and M. Pasta, *Joule*, 2018, **2**, 1950–1960.
- M. Morant-Giner, R. Sanchis-Gual, J. Romero, A. Alberola, L. García-Cruz, S. Agouram, M. Galbiati, N. M. Padial, J. C. Waerenborgh, C. Martí-Gastaldo, S. Tatay, A. Forment-Aliaga and E. Coronado, *Adv. Funct. Mater.*, 2017, **1706125**, 1–11.
- Z. Qin, Y. Li and N. Gu, *Adv. Healthc. Mater.*, 2018, **7**, 1–13.
- S. Ferlay, T. Mallah, R. Ouahès, P. Veillet and M. Verdaguer, *Nature*, 1995, **378**, 701–703.
- L. Trinh, S. Zerdane, S. Mazérat, N. Dia, D. Dragoë, C. Herrero, E. Rivière, L. Catala, M. Cammarata, E. Collet and T. Mallah, *Inorg. Chem.*, 2020, **59**, 13153–13161.
- G. Maurin-Pasturel, J. Long, Y. Guari, F. Godiard, M. G. Willinger, C. Guerin and J. Larionova, *Angew. Chemie - Int. Ed.*, 2014, **53**, 3872–3876.
- L. Cheng, H. Gong, W. Zhu, J. Liu, X. Wang, G. Liu and Z. Liu, *Biomaterials*, 2014, **35**, 9844–9852.
- Y. Yin, Q. Li, S. Ma, H. Liu, B. Dong, J. Yang and D. Liu, *Anal. Chem.*, 2017, **89**, 1551–1557.
- J. D. Qiu, H. Z. Peng, R. P. Liang, J. Li and X. H. Xia, *Langmuir*, 2007, **23**, 2133–2137.
- M. Caminale, L. Anghinolfi, E. Magnano, F. Bondino, M. Canepa, L. Mattera and F. Bisio, *ACS Appl. Mater. Interfaces*, 2013, **5**, 1955–1960.
- G. Armelles, A. Cebollada, A. García-Martín and M. U. González, *Adv. Opt. Mater.*, 2013, **1**, 2–2.
- G. Shemer and G. Markovich, *J. Phys. Chem. B*, 2002, **106**, 9195–9197.
- L. Jing, X. Liang, Z. Deng, S. Feng, X. Li and M. Huang, *Biomaterials*, 2014, **35**, 5814–5821.
- G. Maurin-Pasturel, E. Rascol, M. Busson, S. Sevestre, J. Lai-Kee-Him, P. Bron, J. Long, J. Chopineau, J.-M. Devoisselle, Y. Guari and J. Larionova, *Inorg. Chem. Front.*, 2017, **4**, 1737–1741.
- F. N. Crespiho, V. Zucolotto, C. M. A. Brett, O. N. Oliveira and F. C. Nart, *J. Phys. Chem. B*, 2006, **110**, 17478–17483.
- M. H. Xue, Q. Xu, M. Zhou and J. J. Zhu, *Electrochem. commun.*, 2006, **8**, 1468–1474.
- V. Gadet, T. Mallah, I. Castro, M. Verdaguer and P. Veillet, *J. Am. Chem. Soc.*, 1992, **114**, 9213–9214.
- H. Häkkinen, *Nat. Chem.*, 2012, **4**, 443–455.
- J. Turkevich, *Gold Bull.*, 1985, **18**, 125–131.
- K. M. Mayer and J. H. Hafner, *Chem. Rev.*, 2011, **111**, 3828–3857.
- H. Chen, X. Kou, Z. Yang, W. Ni and J. Wang, *Langmuir*, 2008, **24**, 5233–5237.
- N. R. Jana, L. Gearheart, S. O. Obare and C. J. Murphy, *Langmuir*, 2002, **18**, 922–927.
- M. F. Dumont, E. S. Knowles, A. Guiet, D. M. Pajerowski, A. Gomez, S. W. Kycia, M. W. Meisel and D. R. Talham, *Inorg. Chem.*, 2011, **50**, 4295–4300.
- K. S. Lee and M. A. El-Sayed, *J. Phys. Chem. B*, 2006, **110**, 19220–19225.
- Yu, S.-S. Chang, C.-L. Lee and C. R. C. Wang, *J. Phys. Chem. B*, 1997, **101**, 6661–6664.
- S. Barbosa, A. Agrawal, L. Rodríguez-Lorenzo, I. Pastoriza-Santos, R. A. Alvarez-Puebla, A. Kornowski, H. Weller and L. M. Liz-Marzán, *Langmuir*, 2010, **26**, 14943–14950.