

This item is the archived peer-reviewed author-version of:

Tailoring microstructure and superconducting properties in thick $BaHfO_3$ and $Ba_2Y(Nb/Ta)O_{6-x}$ doped YBCO films on technical templates

Reference:

Sieger Max, Pahlke Patrick, Lao Mayraluna, Eisterer Michael, Meledin Alexander, Van Tendeloo Gustaaf, Ottolinger Rick, Haenisch Jens, Holzapfel Bernhard, Usoskin Alexander,- Tailoring microstructure and superconducting properties in thick $BaHfO_3$ and $Ba_2Y(Nb/Ta)O_{6-x}$ doped YBCO films on technical templates
IEEE transactions on applied superconductivity / IEEE [New York, N.Y.] - ISSN 1051-8223 - 27:4(2017), 6601407
Full text (Publishers DOI): <http://dx.doi.org/doi:10.1109/TASC.2016.2644858>
To cite this reference: <http://hdl.handle.net/10067/1419610151162165141>

Tailoring microstructure and superconducting properties in thick BaHfO₃ and Ba₂Y(Nb/Ta)O₆ doped YBCO films on technical templates

Max Sieger, Patrick Pahlke, Mayraluna Lao, Michael Eisterer, Alexander Meledin, Gustaaf Van Tendeloo, Rick Ottolinger, Jens Hänisch, Bernhard Holzapfel, Alexander Usoskin, Ahmed Kursumovic, Judith L. MacManus-Driscoll, Benjamin H. Stafford, Markus Bauer, Kornelius Nielsch, Ludwig Schultz, Ruben Hühne

Abstract — The current transport capability of YBa₂Cu₃O_{7-x} (YBCO) based coated conductors (CCs) is mainly limited by two features: the grain boundaries of the used textured template, which are transferred into the superconducting film through the buffer layers, and the ability to pin magnetic flux lines by incorporation of defined defects in the crystal lattice. By adjusting the deposition conditions, it is possible to tailor the pinning landscape in doped YBCO in order to meet specific working conditions (T , B) for CC applications. To study these effects, we deposited YBCO layers with a thickness of about 1-2 μm using pulsed laser deposition on buffered rolling-assisted biaxially textured Ni-W substrates as well as on metal tapes having either an ion-beam textured YSZ buffer or an MgO layer textured by inclined substrate deposition. BaHfO₃ and the mixed double-perovskite Ba₂Y(Nb/Ta)O₆ were incorporated as artificial pinning centers in these YBCO layers. X-ray diffraction confirmed the epitaxial growth of the superconductor on these templates as well as the biaxially oriented incorporation of the secondary phase additions in the YBCO matrix. A critical current density J_c of more than 2 MA/cm² was achieved at 77 K in self-field for 1-2 μm thick films. Detailed TEM studies revealed that the structure of the secondary phase can be tuned, forming c -axis aligned nanocolumns, ab -oriented platelets or a combination of both. Transport measurements show that the J_c anisotropy in magnetic fields is reduced by doping and the peak in the $J_c(\theta)$ curves can be correlated to the microstructural features.

Index Terms— ABAD, coated conductors, ISD, pinning, pulsed laser deposition, RABiTS, YBCO

I. INTRODUCTION

YBa₂Cu₃O_{7-x} (YBCO) and related compounds are the basic materials for the realization of coated conductor (CC) applications. High-temperature superconductor (HTS) layers can be grown epitaxially onto different substrates by a number of physical and chemical deposition techniques, e.g. metal-organic chemical vapor deposition [1], electron-beam evaporation [2], pulsed laser deposition (PLD) [3]-[6] or chemical solution deposition [7]-[10]. Since grain boundaries (GBs) and texture are transferred by epitaxial growth into the HTS matrix, highly-oriented substrates/buffer layers are essential for high- J_c performance of the functional layer in the low-field region, where GBs act as current blockers [11]-[15].

Over the last 20 years, significant efforts have been made to develop biaxially textured templates for long length conductor manufacture [16]. One of the technological approaches is the preparation of biaxially textured buffer layers on arbitrarily textured metal tapes by methods like ion-beam assisted deposition (IBAD) [17],[18], alternating beam assisted deposition (ABAD) [19] or inclined substrate deposition (ISD) [20]. Alternatively, highly textured metal templates are realized by the rolling-assisted biaxially textured substrate (RABiTS) approach [21]-[24].

More recently, significant efforts have been devoted to enhance the current transport capability of the superconducting layers in magnetic fields. A variety of secondary particles were introduced into the YBCO matrix as perovskite-type BaMO₃ ($M = \text{Zr, Hf, Sn, ...}$) compounds [2],[6-8],[25-30] or double-perovskite oxides as Ba₂YNbO₆ [31-32] or mixed Ba₂Y(Nb_{0.5}Ta_{0.5})O₆ (BYNTO) [33-36] to enhance vortex pinning and increase J_c in high magnetic fields. A so-called nano-engineering, i.e. tailoring the amount, shape, size and arrangement of artificial pinning centers (APCs), gives the possibility to tune the $J_c(B, \theta)$ characteristic of a YBCO film to meet specific working conditions, e.g. wires at 77 K and ≤ 1 T, wind turbines (30 K, ~ 3 -5 T) and high-field magnets (4.2 K, > 5 T), making pinning-enhanced YBCO CCs superior to conventional superconducting wires.

In this work we investigate thick BaHfO₃ (BHO) and BYNTO-doped YBCO films deposited by PLD on buffered

This work was supported by EUROTAPES, a collaborative project funded by the European Commission's Seventh Framework Program (FP7 / 2007 - 2013) under Grant Agreement n.280432. (Corresponding author: M. Sieger)

M. Sieger, P. Pahlke, R. Ottolinger, K. Nielsch and L. Schultz are with IFW Dresden, 01069 Dresden, Germany and also with Dresden University of Technology, 01062 Dresden, Germany (e-mail: m.sieger@ifw-dresden.de).

M. Lao and M. Eisterer are with Atominstytut, TU Wien, 1020 Vienna, Austria (e-mail: michael.eisterer@tuwien.ac.at).

A. Meledin and G. V. Tendeloo are with Electron microscopy for materials science (EMAT), University of Antwerp, 2020 Antwerp, Belgium (e-mail: staf.vantendeloo@uantwerpen.be).

J. Hänisch and B. Holzapfel are with the Karlsruhe Institute of Technology, Germany (e-mail: bernhard.holzapfel@kit.edu).

A. Usoskin is with Bruker HTS GmbH, 63755 Alzenau, Germany (e-mail: alexander.usoskin@bruker-hts.com).

A. Kursumovic and J. MacManus-Driscoll are with the University of Cambridge, Cambridge CB3 0FZ, U.K. (e-mail: jld35@cam.ac.uk).

B. H. Stafford is with THEVA Dünnschichttechnik GmbH, 85737 Ismaning, Germany, IFW Dresden, 01069 Dresden, Germany and also with Dresden University of Technology, 01062 Dresden, Germany (e-mail: stafford@theva.com).

M. Bauer is with THEVA Dünnschichttechnik GmbH, 85737 Ismaning, Germany (e-mail: bauer@theva.com).

R. Hühne is with IFW Dresden, 01069 Dresden, Germany (e-mail: R.Huehne@ifw-dresden.de).

ABAD-YSZ templates, Ni-5at% W RABiTS substrates, as well as on ISD-MgO buffered Hastelloy tapes. We discuss the influence of growth rate, substrate temperature and doping level on the microstructure and electrical properties of the superconducting layer by means of electron microscopy, X-Ray diffraction, transport current measurements and scanning Hall probe microscopy (SHPM).

II. EXPERIMENTAL DETAILS

A. Sample preparation

YBCO films with a thickness of more than 1 μm containing either up to 15 mol% of BaHfO₃ (BHO:YBCO) or 5 mol% of the mixed double-perovskite Ba₂Y(Nb_{0.5}Ta_{0.5})O₆ (BYNTO:YBCO) were deposited on technical substrates by pulsed laser deposition from premixed targets. A Lambda Physics LPX305Pro KrF excimer laser ($\lambda = 248 \text{ nm}$) was applied with varying repetition rates leading to a growth rate R of 0.4 to 8 nm/s. More details can be found in Ref. [25],[26]. Three major types of coated conductor templates were studied, i.e. ABAD-YSZ-buffered stainless steel tape (ABAD) with a CeO₂ cap layer [37], CSD-La₂Zr₂O₇/CeO₂-buffered biaxially-textured Ni-5 at% W tape (RABiTS Ni-W, [35]), and ISD-MgO buffered Hastelloy tape with a 300 nm thin GdBa₂Cu₃O₇ seed layer [38]. The substrate temperature T_s was varied between 770 and 840°C via a resistive heater. A silver cap layer was deposited by PLD for surface protection and lower contact resistance during transport measurements.

B. Structural characterization

X-ray diffraction was carried out on a Bruker D8 Advance Diffractometer (Co-K α radiation). High-angle annular dark field scanning transmission electron microscopy (HAADF-STEM), annular dark field scanning transmission electron microscopy (ADF-STEM) and energy-dispersive X-Ray spectroscopy (EDX) mappings were performed on an FEI Tecnai Osiris microscope operated at 200 kV as well as on an FEI Titan “cubed” electron microscope operated at 200 kV and 300 kV.

C. Electrical characterization

The critical temperature $T_{c,90}$ was measured inductively (transition width $\Delta T_c = T_{c,90} - T_{c,10}$). Maps for the critical current density (J_c) distribution in the sample were obtained by inversion of the trapped field profile measured by a scanning Hall probe device (scanning Hall probe microscopy, SHPM, [39]) in liquid N₂ (77 K). The listed values correspond to the self-field (sf) critical current density $J_{c,sf}$. Angle-resolved critical current density measurements in magnetic fields, $J_c(B, \theta)$, were carried out by either using a vector vibrating sample magnetometer (VSM) or by transport measurements. The latter were conducted in maximum Lorentz force configuration in a four-point measurement assembly using laser-cut bridges of 800 μm length and 300 to 500 μm width. Here, J_c is defined by an electrical field criterion of 1 $\mu\text{V}/\text{cm}$. In both cases, θ is the angle between the magnetic field \vec{B} and the sample normal \vec{n} ($\vec{B} \parallel \vec{n}$ for 0° and 180°, $\vec{B} \perp \vec{n}$ for 90°).

III. RESULTS AND DISCUSSION

A. Films on ABAD-YSZ

YBCO samples with 6 mol% BHO (2.6 vol%) and 5 mol% BYNTO (4.7 vol%) respectively were deposited on ABAD-YSZ substrates using $T_s = 790$ to 830°C and $R = 0.4$ to 1.3 nm/s. At first, we start to discuss samples prepared with standard deposition conditions ($T_s = 810^\circ\text{C}$, $R = 1.3 \text{ nm/s}$) having a film thickness $\sim 1.2 \mu\text{m}$. Typical results of the structural and electrical characterization are summarized in Table I for those samples. The θ -2 θ scans reveal a pure c -axis growth of YBCO, BHO and BYNTO. It was proven by texture measurements and TEM analysis that BHO and BYNTO are incorporated biaxially textured into the YBCO matrix resulting in an elongation of c_{YBCO} (see Table I). Compared to $T_c = 89.0 \text{ K}$ for the undoped sample, T_c is lower in the BHO-doped film (87.5 K), but higher for the BYNTO sample (91.0 K). $J_{c,sf}$ (77 K) is reduced to about 40% of the value of pure YBCO by doping with BHO, but almost not changed by doping with BYNTO. We find a comparatively high density of nanosized Y₂O₃ platelets in pristine YBCO, which is usual for our films [37]. The amount of Y₂O₃ is strongly reduced by BHO additions. In contrast, a increased concentration was detected in the BYNTO samples (see Fig. 1).

TABLE I
STRUCTURAL AND ELECTRICAL PROPERTIES OF PRISTINE YBCO, BHO:YBCO AND BYNTO:YBCO FILMS ON ABAD-YSZ ($T_s = 810^\circ\text{C}$, $R = 1.3 \text{ nm/s}$)

Parameter	YBCO	BHO:YBCO	BYNTO:YBCO
YBCO c -axis, Å	11.72	11.76	11.74
$T_{c,90} (\Delta T_c)$, K	89.0 (1.0)	87.5 (2.0)	91.0 (2.0)
$J_{c,sf}$ (77 K), MA/cm ²	2.3±0.2	0.8±0.2	2.1±0.2
Y ₂ O ₃ precipitates	present [37]	reduced	increased

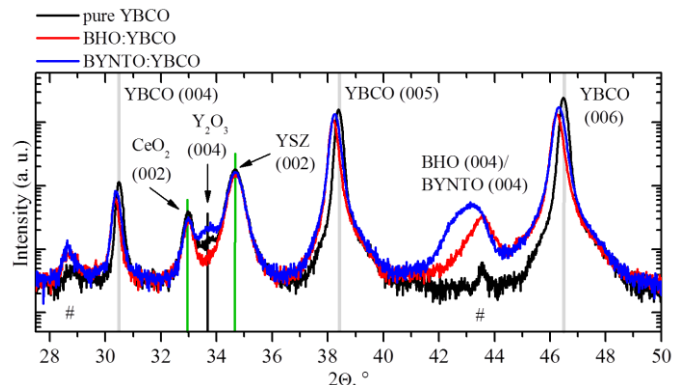


Fig. 1. θ -2 θ scans for YBCO, BHO:YBCO and BYNTO:YBCO deposited on ABAD-YSZ at $T_s = 810^\circ\text{C}$ and $R = 1.3 \text{ nm/s}$ (# denote peaks from the underlying metal tape).

We found that the local microstructure and therefore the J_c anisotropy are sensitive to deposition conditions such as growth rate (R) and substrate temperature (T_s). The microstructure for different R is shown in Fig. 2 as one example. Aside from the BHO nanostructures, we will focus on defect structures like YBa₂Cu₄O₈ (Y-124) intergrowths and nanometer-sized Y₂O₃ precipitates. At low R , BHO grows as almost pure fan-shaped nanocolumns. By increasing R , BHO columns become straighter so that fan-shaped and straight parts coexist. It was shown before that the splay of BaZrO₃

nanocolumns is also influenced by the substrates temperature [40] and surface [41].

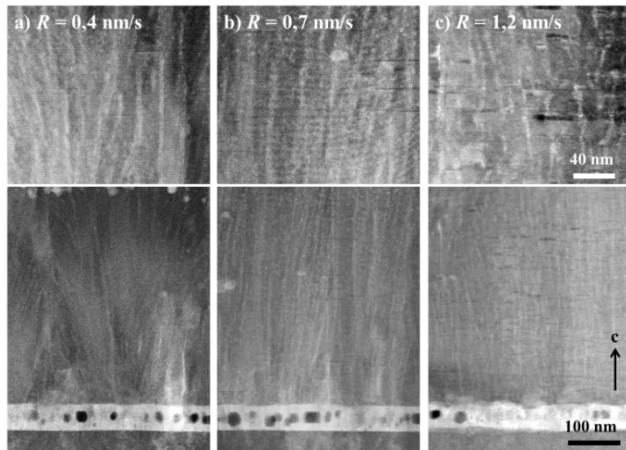


Fig. 2. ADF-STEM images of BHO:YBCO samples on ABAD-YSZ prepared at $T_s \sim 800^\circ\text{C}$ and growth rates of $R = 0.4, 0.7$ and 1.2 nm/s. Top: BHO:YBCO bulk region (higher magnification). Bottom: BHO:YBCO/tape interface region. The dark spots in the bright CeO_2 -layer are Ba-rich precipitates.

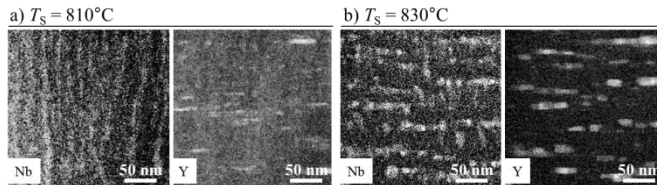


Fig. 3. STEM-EDX elemental mappings of Nb and Y for BYNT0:YBCO samples deposited at 810°C (a) and 830°C (b) on ABAD-YSZ using a deposition rate of $R = 1.3$ nm/s.

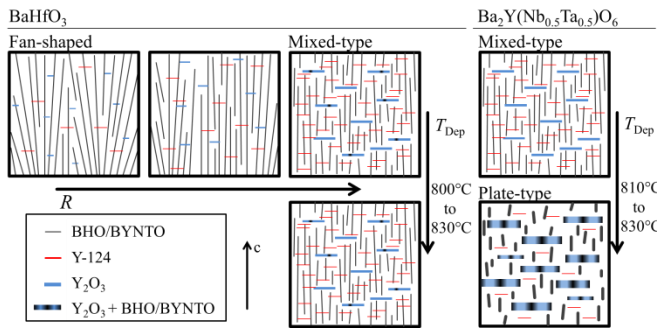


Fig. 4. Scheme of different types of defect structure for BHO and BYNT0 doped YBCO films deposited on ABAD-YSZ templates at growth rate $R = 0.4-1.3$ nm/s and temperatures $T_s = 800-830^\circ\text{C}$.

The density of Y-124 intergrowth is low and Y_2O_3 platelets with a size <10 nm are dispersed in the YBCO matrix. At $R > 1$ nm/s, the c -axis aligned BHO columns get shorter and the amount of ab -aligned Y_2O_3 platelets is increased. The local microstructure is generally more disordered and the density of Y-124 intergrowths is higher compared to deposition at lower growth rates. The mixture of ab -aligned and c -axis aligned nanostructures was already shown by Ercolano et al. [33] and will be called “mixed-type” structure in the following discussion.

A microstructure, which is similar to that of BHO:YBCO at $R > 1$ nm/s, was also found in BYNT0:YBCO samples using a

similar temperature, $T_s = 810^\circ\text{C}$, and growth rate, $R = 1.3$ nm/s (compare Fig. 2(c) and 3(a)).

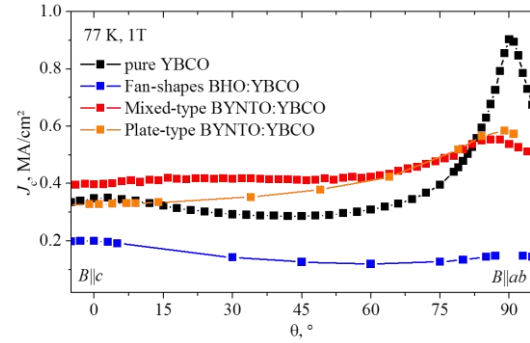


Fig. 5. Angular dependence of the critical current density, $J_c(\theta)$, at 77 K / 1 T of fan-shaped BHO:YBCO and mixed-type and plate-type BYNT0:YBCO samples deposited on ABAD-YSZ.

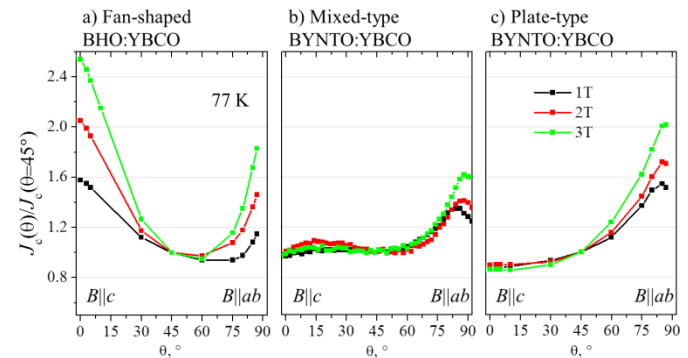


Fig. 6. Angular dependence of the critical current density, $J_c(\theta)$, of fan-shaped BHO:YBCO (a), mixed-type BYNT0:YBCO (b) and plate-type BYNT0:YBCO samples deposited on ABAD-YSZ. Data for (a) and (c) were obtained by VSM measurements, for (b) by transport measurement. J_c data were taken at 77 K and normalized to $J_c(\theta = 45^\circ)$.

Here, a mixed-type structure is formed consisting of >100 nm long BYNT0 columns and about 10 nm \times 20 nm large Y_2O_3 platelets (Fig. 3 a). When increasing T_s by about 20 K, the density and length of the c -axis oriented BYNT0 columns as well as the density of Y-124 intergrowth is significantly reduced whereas 20 nm \times 50 nm sized BYNT0/ Y_2O_3 mixed ab -aligned platelets are formed (plate-type, Fig. 3 (b)). In contrast, the microstructure did not change significantly for higher T_s in the BHO doped samples. As a summary of these observations, Fig. 4 presents a schematic overview, how number, size and orientation of dopant, Y-124 and Y_2O_3 change with increasing R and T_s .

Fig. 5 gives the anisotropy curves at 77 K, 1 T for a fan-shape type BHO sample as well as the mixed-type and plate-type BYNT0 samples in comparison with undoped YBCO. The absolute values of $J_c(\theta)_{\min}$ for the BYNT0-doped films are higher than in the undoped sample. At these conditions the J_c -performance of the fan-shaped BHO-doped sample is lower compared to the undoped sample. The situation is different at lower temperatures and higher field (40 K / 4 T), where this type of pinning centers was found to be more effective [26].

Fig. 6 summarizes the corresponding normalized J_c anisotropy curves at 77 K: The fan-shaped BHO nanocolumns create a broad peak in $J_c(\theta)$ at $B \parallel c$ (Fig. 6(a)). A detailed discussion of the $J_c(B, \theta, T)$ -behavior is given in Ref. [26].

In the mixed-type BYNTO sample, where c -axis correlated defects and ab -aligned BYNTO/ Y_2O_3 platelets are present, only small peaks at $B||c$ and $B||ab$ are found in the anisotropy curve (Fig. 6(b)). In general, J_c is enhanced over a wide angular range whereas the anisotropy $J_c(\theta)_{\max} / J_c(\theta)_{\min}$ is well below two for fields up to 3 T in the measured temperature range of 40 to 77 K. This might be a result of the simultaneously acting c -axis and ab -axis aligned defects, leading to enhanced pinning at angles θ between 0° and 90° (staircase model in Ref. [33]). $J_{c,\min}$ is enhanced by more than 50% compared to similar undoped samples especially at $T < 77$ K (data not shown).

In contrast, the BYNTO:YBCO sample prepared at higher T_s exhibits a strong and broad peak for $B||ab$ and virtually no peak for $B||c$ (Fig. 6(c)). This might be explained by the fact that almost no c -axis correlated defects are present, whereas a high number of ab -aligned BYNTO/ Y_2O_3 platelets are found.

B. Films on RABiTS Ni-W

Doped YBCO films on buffered Ni-W tapes show a similar microstructure to that of films on ABAD-YSZ tapes with the exception of the additional global grain network arising from the template (~ 20 to $50 \mu\text{m}$ diameter grains on Ni-W, $< 1 \mu\text{m}$ on ABAD-YSZ [42]). Strong $(00l)$ peaks in XRD measurements (data not shown) indicate a highly c -axis oriented growth; additional peaks of the dopant material appear for the 5 mol% BHO (2.2 vol%) and BYNTO doped samples. The 15 mol% BHO (6.9 vol%) doped sample shows an asymmetric BHO peak shape which might be associated with the incorporation of Y in BHO or Hf in Y_2O_3 , respectively [25],[43],[44]. The biaxially oriented BHO nanoparticles lead to an elongation of the YBCO c -axis, a reduction of T_c and a suppression of the Y_2O_3 formation. In comparison, BYNTO-doped films exhibit only a slight increase in c -axis length, slightly decreased T_c and a preferred formation of Y_2O_3 (Tab. II) as on ABAD-YSZ (Tab. I)

In BYNTO doped YBCO films on Ni-W the used growth conditions lead to a mixed-type structure of c -axis aligned BYNTO columns and ab -aligned Y_2O_3 platelets (partly with Nb and Ta additions, Fig. 7(a)) similar to films on ABAD-YSZ (cf. Fig. 3(b)). The local microstructure of the 5 mol% BHO doped samples is similar to that observed for ABAD-YSZ based films (Fig. 2(c)). At $T_s = 830^\circ\text{C}$ and growth rates of $R \sim 1.6 \text{ nm/s}$, c -axis aligned columns are formed (Fig. 7(b)). A higher content of 15 mol% BHO leads to the formation of incomplete BHO and/or Y_2O_3 layers within the YBCO matrix mainly parallel to the ab -plane (Fig. 7(c)). A minor BHO component of c -axis oriented columns with a fan-shaped structure is also present in these samples. In addition to the deposition parameters, the microstructure might depend on the vicinal angle of the underlying substrate [42],[43]. As the grains on RABiTS Ni-W exhibit an individual tilt of the Ni-W [001] direction towards the tape normal, an additional grain to grain variance of the microstructure cannot be excluded.

This particular microstructures lead to a specific in-field current transport behavior. Figures 7 (d)-(f) show normalized anisotropy curves at 77 K for magnetic fields up to 3 T, where $J_c/J_c(\theta=45^\circ)$ is a measure for the strength of correlated pinning centers parallel to the c -axis ($\theta = 0^\circ$) and ab -planes

($\theta = 90^\circ$). All samples show only weak c -axis correlated pinning at 77 K in the examined magnetic field range up to 3 T, i.e. $J_c^{B||c}/J_c(45^\circ) \sim 1$, as is apparent in the $J_c(\theta)$ curve at 77 K at 1 T (Fig. 8(a)). Whereas BYNTO doped and low BHO concentration YBCO films show moderate pinning for $B||ab$ (~ 2.5), the highly BHO-doped film with ab -parallel platelets exhibits a strong anisotropy, i.e. $J_c^{B||ab}/J_c(45^\circ)$ ranges up to 15 at 3 T.

TABLE II
STRUCTURAL AND ELECTRICAL PROPERTIES OF PRISTINE YBCO, BHO:YBCO AND BYNTO:YBCO FILMS PREPARED WITH STANDARD CONDITIONS ON Ni-5W

Parameter	YBCO	+5BYNTO	+5BHO	+15BHO
YBCO c -axis, Å	11.69	11.71	11.72	11.74
$T_{c,90} (\Delta T_c)$, K	90.4 (1.2)	90.1 (1.0)	88.3 (0.8)	88.0 (2.1)
Y_2O_3 precipitates	present	increased	reduced	reduced

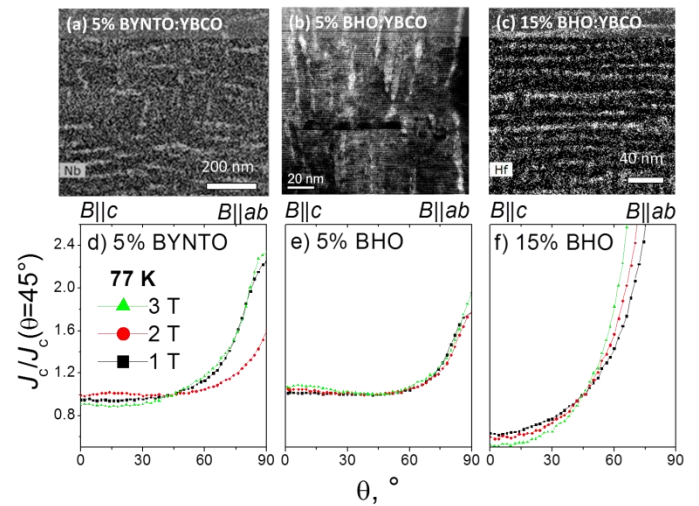


Fig. 7. Spatial distribution of BYNTO and BHO in 5 mol% BYNTO (a), 5 mol% BHO (b) and 15 mol% BHO doped (c) YBCO films, observed as bright contrast in HAADF-STEM (b) and STEM-EDX elemental mappings with respective normalized J_c anisotropy curves at 77 K for several magnetic fields (d)-(f) (All films deposited at 830°C on Ni5W, $R = 1.6 \text{ nm/s}$).

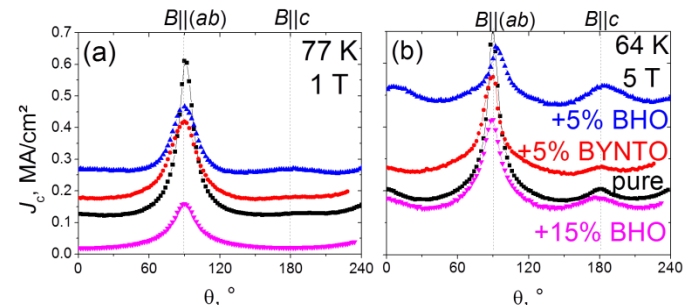


Fig. 8. Angular dependence of J_c at 77 K / 1 T (a) and 64 K / 5 T (b) for pure YBCO, BYNTO, low BHO and highly BHO doped YBCO films deposited at 830°C on Ni5W, $R = 1.6 \text{ nm/s}$.

TABLE III
ANISOTROPY $J_{c,\max} / J_{c,\min}$ OF PRISTINE YBCO, BHO:YBCO AND BYNTO:YBCO FILMS PREPARED WITH STANDARD CONDITIONS ON RABiTS Ni-W

Measurement conditions	YBCO	+5BYNTO	+5BHO	+15BHO
77 K / 1 T	5.1	2.5	1.8	8.4
64 K / 5 T	4.2	2.2	1.4	1.2

The J_c measurements at 77 K, 1 T (Fig. 8(a)) and 64 K, 5 T (Fig. 8(b)) show a decreased anisotropy $A = J_{c,max}/J_{c,min}$ (cf. Table III) for all doped films on RABiTS Ni-W compared to the pure YBCO as desired for specific applications such as superconducting magnets. At 77 K / 1 T both low-doped films perform better than pure YBCO in a wide angular range. The 15 mol% BHO doped YBCO shows reduced J_c values in the full angular range with a high anisotropy ($A = 8.4$). The reduced J_c values might be due to the broad ΔT_c and small irreversibility fields H_{irr} in c -direction.

At lower temperatures, the nanosized structures lead to characteristic pinning effects for magnetic fields with an additional broad peak for $B||c$. The highly-BHO doped sample almost reaches the J_c level of pure YBCO. The critical current density of the 5% BYNTO-doped YBCO is significantly increased in a wide angular range compared to pure YBCO by the wide-angle pinning ability of the mixed-type structures. The peak for $B||c$ of the 5% BHO:YBCO film is massively increased by the c -axis oriented BHO nanocolumns. This sample shows the best performance with a high J_c level in the full angular range.

C. Films on ISD-MgO

Although we were able to grow high-quality YBCO films with c -axis oriented nanostructures on textured metal tapes and textured ABAD-based buffer layers by proper adjustment of the growth parameters T and R , these results are not directly transferable to PLD-BHO:YBCO films on ISD-MgO buffered templates, which have an inherent tilt of the [001] direction away from the tape normal of $\sim 30^\circ$. The epitaxial, yet tilted growth (proven by pole figure measurements, not shown here) of the BHO:YBCO film on such substrates leads to the formation of a layered structure parallel to the ab -plane adopting the tilt angle of the template (Fig. 9 (a)). The elemental mapping for Y, Cu and Hf (Fig. 9 (b)+(c)) indicates a stacking of YBCO layers and BHO/ Y_2O_3 platelets. An incorporation of Hf in Y_2O_3 or Y in BHO cannot be excluded from these data.

In order to understand the growth mode on ISD templates, BHO:YBCO films have been grown on vicinal-cut SrTiO₃ single crystals with vicinal angles α from 0 to 40° [43]. Whereas BHO:YBCO films on flat (0°) STO substrates exhibit columnar BHO structures parallel to c_{YBCO} , low miscut angles (2 to 10°) lead to mixed-type structures similar to Fig. 3 and Fig. 7(a). This is also in accordance with results of Baca et al. studying thin BaZrO₃-doped YBCO films on vicinal tilted single crystals [41],[45]. Even higher angles α lead to tilted BHO/ Y_2O_3 platelets as observed for BHO:YBCO/ISD-MgO. Such structures were found to significantly decrease J_c values in longitudinal direction and increase the anisotropy by current blocking behavior [46].

For BHO:YBCO films on ISD-MgO different deposition parameters were varied to test if a different distribution of the incorporated pinning centers can be realized. It was found that the thickness and distance of the BHO/ Y_2O_3 layers can be adjusted by the doping content and the temperature T_S . A higher growth temperature leads to enhanced diffusion and thereby wider separation (distance d) between the platelet regions (Fig. 10), whereas the thickness t of these platelets is barely influenced (Table IV).

TABLE IV
THICKNESS AND DISTANCE OF BHO/ Y_2O_3 PLATELETS IN BHO:YBCO FILMS ON ISD-MGO TAPES

BHO CONTENT, MOL%	DEPOSITION TEMPERATURE, °C	DISTANCE, NM	THICKNESS, NM	$T_{c,90}(\Delta T_c)$, K
5	810	80-90	15	88.8 (1.1)
10	770	30	5-6	87.9 (0.8)
10	810	50	5-10	88.7 (1.6)
10	840	75	7-10	88.3 (2.1)

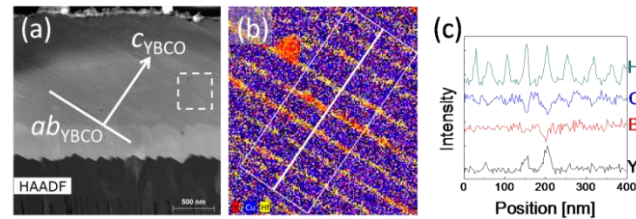


Fig. 9. HAADF-STEM image (a) together with STEM-EDX mapping (b) and integrated element line scan of Hf, Cu, Ba, Y (green, blue, red and black respectively) (c) of 10 mol% BHO:YBCO on ISD-MgO. (HAADF STEM image showing the mapped area by a white square, the composite STEM-EDX mapping showing the area of the integrated line scan by a white rectangle.)

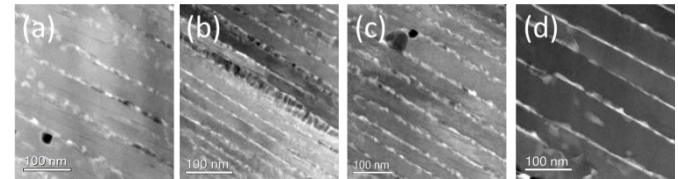


Fig. 10. ADF-STEM images of a 5 mol% BHO:YBCO films deposited at 810°C (a), 10 mol% BHO / 770°C (b), 10 mol% BHO / 810°C (c), 10 mol% BHO / 840°C (d) on ISD-MgO.

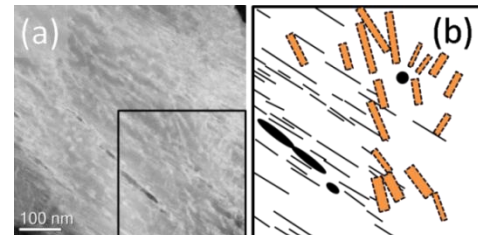


Fig. 11. ADF-STEM image of a 5% BHO:YBCO film on ISD-MgO (a) (deposition conditions $T_S = 770^\circ\text{C}$, $R = 5.4$ nm/s). The microstructural features of the inset are sketched (b) including large Y_2O_3 precipitates (black ellipsoids), extra CuO_2 chains (black lines) and short BHO columns (orange rectangles).

Doubling the BHO content in the YBCO matrix at the same T_S leads to almost half the distance t between adjacent BHO platelets. Higher growth rates R tilt the BHO platelets towards the c_{YBCO} (Fig. 11, BHO sketched as orange rectangles in Fig. 11(b)). Additionally a lot of extra CuO_2 planes (i.e. Y-124) as well as some larger Y_2O_3 agglomerates appear. At very high R (8 nm/s) a highly lamellar growth in the direction of the substrate normal leads to porous films by shadowing effects (not shown here). All three parameters do not influence the c -axis length ($\sim 11.8 \text{ \AA}$) and do only marginally decrease T_c from the value of a pure YBCO film on ISD-MgO ($T_S = 810^\circ\text{C}$, $R = 1.6$ nm/s) with $T_{c,90} = 89.5$ K, $\Delta T_c = 0.9$ K (cf. Table IV).

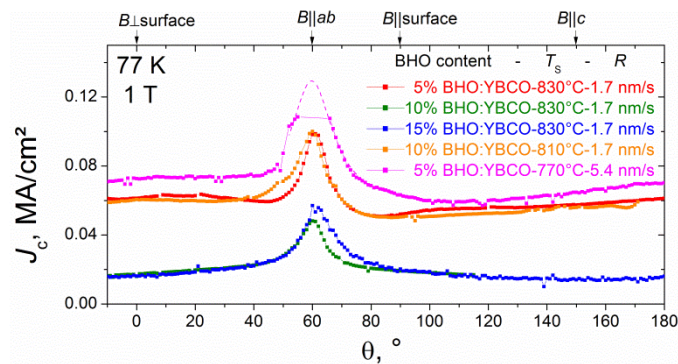


Fig. 12. Critical current anisotropy, $J_c(\theta)$, at 77 K, 1 T for PLD-BHO:YBCO films with different BHO contents on ISD-MgO templates deposited at different T_s and R (color code according to Ref. [2], purple curve fitted by a Lorentz function for $\theta = 55$ to 65° as J_c exceeded the measurement current of the set-up).

The critical current anisotropy curves (Fig. 12) are highly influenced by the deposition conditions T_s , R and the BHO content of the BHO:YBCO films. All films show a strong ab -plane correlated pinning behavior. Medium (10%, green) and high (15%, blue) BHO levels show lower absolute J_c values than the low doped (5%, red) BHO:YBCO film. This is comparable to films deposited by electron-beam evaporation (cf. Stafford et al. [2], 4.5 mol%, 8.6 mol% and 12.9 mol% BHO:YBCO, same color code). The $J_c(\theta)$ curves of medium (green) and high BHO:YBCO (blue) are symmetrical to the ab -peak. The high- R sample (purple) exhibits a plateau between B_{\perp} surface and $B_{\parallel ab}$, probably caused by pinning-active particle species tilted off the ab -plane (cf. Fig. 11). The same argument holds for the low BHO:YBCO (red) sample that shows a broad peak around $\theta \sim 15$ to 20° , and the medium-BHO:YBCO sample deposited at reduced T_s (orange), where decreased diffusion might form pinning species off the ab -plane.

CONCLUSION

As the presented results show, it is possible to tailor the microstructure in thick BHO and BYNTO doped YBCO films on technical templates by careful adjustment of key parameters such as substrate temperature T_s , growth rate R and doping level. On ABAD-YSZ templates we were able to create pinning centers acting effectively for $B_{\parallel c}$ or $B_{\parallel ab}$. Moreover a mixed type could be realized with low J_c anisotropy, which is explained by the observed microstructure. Similar microstructures were found on Ni5-W templates. Low doping contents of BHO and BYNTO (5 mol%) lead to either c -axis aligned or mixed-type structures with improved $J_c(\theta)$ performance. A higher concentration of BHO results in BHO/ Y_2O_3 platelets oriented parallel to the ab -plane. This sample shows an increased anisotropy at high temperatures. The growth of APCs on ISD-MgO-based templates is mainly influenced by the lattice tilt of the substrate that is inherited by the YBCO layer, which leads to layered structures parallel to the ab -planes. It is possible to change the distance of such planes by growth temperature and doping level, the orientation is dependent on diffusion processes and therefore R and T_s . Short and strongly splayed BHO nanocolumns are formed at

high growth rate and low substrate temperature leading to superior $J_c(\theta)$ behavior.

ACKNOWLEDGMENT

The authors would like to thank M. Falter of Deutsche Nanoschicht GmbH for providing the buffered Ni5W template and M. Kühnel, J. Scheiter and R. Nast for technical assistance.

REFERENCES

- [1] V. Selvamanickam, Y. Chen, T. Shi, Y. Liu, N. D. Khatri, J. Liu, Y. Yao, X. Xiong, C. Lei, S. Soloveichik, E. Galstyan, and G. Majkic, "Enhanced critical currents in (Gd,Y)Ba₂Cu₃O_x superconducting tapes with high levels of Zr addition", *Supercond. Sci. Technol.*, vol. 26, Jan. 2013, Art. No. 035006.
- [2] B. Stafford, M. Sieger, O. Troshyn, R. Nast, M. Döblinger, R. Hühne, M. Bauer, B. Holzapfel, and L. Schultz, "Pinning Centres in ISD-MgO Coated Conductors via EB-PVD", *IEEE Trans. Appl. Supercond.*, vol. 26, no. 3, 2016, Art. No. 6601105.
- [3] X. D. Wu, D. Dijkkamp, S. B. Ogale, A. Inam, E. W. Chase, P. F. Miceli, C. C. Chang, J. M. Tarascon, and T. Venkatesan, "Epitaxial ordering of oxide superconductor thin films on (100) SrTiO₃ prepared by pulsed laser evaporation", *Appl. Phys. Lett.*, vol. 51, no. 11, 861-863, 1987.
- [4] M. Peurla, H. Huhtinen, P. Paturi, Yu P. Stepanov, J. Raittila, and R. Laiho, "YBCO Films Prepared by PLD Using Nanocrystalline Targets Doped With BaZrO₃ or Y₂Ti₁₁", *IEEE Trans. Appl. Supercond.*, vol. 15, no. 2, 2005.
- [5] A. Usoskin and H. C. Freyhardt, "YBCO-Coated Conductors Manufactured by High-Rate Pulsed Laser Deposition", *MRS Bulletin*, vol. 29, no. 8, 583-589, 2004.
- [6] M. Sieger, J. Hänisch, K. Iida, U. Gaitzsch, C. Rodig, L. Schultz, B. Holzapfel, and R. Hühne, "Pulsed laser deposition of thick BaHfO₃-doped YBa₂Cu₃O_{7-δ} films on highly alloyed textured Ni-W tapes", *J. Phys.: Conf. Ser.*, vol. 507, 2014, Art. No. 022032.
- [7] S. Engel, T. Thersleff, R. Hühne, L. Schultz, and B. Holzapfel, "Enhanced flux pinning in YBa₂Cu₃O₇ layers by the formation of nanosized BaHfO₃ precipitates using the chemical deposition method", *Appl. Phys. Lett.*, vol. 90, Feb. 2007, Art. No. 102505.
- [8] M. Erbe, J. Hänisch, T. Freudenberg, A. Kirchner, I. Mönch, S. Kaskel, L. Schultz, and B. Holzapfel, "Improved REBa₂Cu₃O_{7-x} (RE = Y, Gd) structure and superconducting properties by addition of acetylacetone in TFA-MOD precursor solutions", *Journal of Materials Chemistry A*, vol. 2, 4932-4944, Jan. 2014.
- [9] M. Coll, R. Guzman, P. Garcés, J. Gazquez, V. Rouco, A. Palau, S. Ye, C. Magen, H. Suo, H. Castro, T. Puig, and X. Obradors, "Size-controlled spontaneously segregated Ba₂YTaO₆ nanoparticles in YBa₂Cu₃O₇ nanocomposites obtained by chemical solution deposition", *Supercond. Sci. Technol.*, vol. 27, Jan. 2014, Art. No. 044009.
- [10] P. Cayado, K. De Keukeleere, A. Garzón, L. Perez-Mirabet, A. Meledin, J. De Roo, F. Vallés, B. Mundet, H. Rijckaert, G. Pollefeyt, M. Coll, S. Ricart, A. Palau, J. Gázquez, J. Ros, G. Van Tendeloo, I. Van Driessche, T. Puig, and X. Obradors, "Epitaxial YBa₂Cu₃O_{7-x} nanocomposite thin films from colloidal solutions", *Supercond. Sci. Technol.*, vol. 28, Nov. 2015, Art. No. 124007.
- [11] D. T. Verebelyi, D. K. Christen, R. Feenstra, C. Cantoni, A. Goyal, D. F. Lee, M. Paranthaman, P. N. Arendt, R. F. De Paula, J. R. Groves, and C. Prouteau, "Low angle grain boundary transport in YBa₂Cu₃O_{7-δ} coated conductors", *Appl. Phys. Lett.*, vol. 76, No. 13, 1755-1757, March 2000.
- [12] J. H. Durrell, M. J. Hogg, F. Kahlmann, Z. H. Barber, M.G. Blamire, and J. E. Evetts, "Critical Current of YBa₂Cu₃O_{7-δ} Low-Angle Grain Boundaries", *PRL*, Vol. 90, No. 24, June 2003, Art. No. 247006.
- [13] J. H. Durrell and N. A. Rutter, "Importance of low-angle grain boundaries in YBa₂Cu₃O_{7-δ} coated conductors", *Supercond. Sci. Technol.*, Vol. 22, 013011 2009.
- [14] D. Dimos, P. Chaudhari, J. Mannhart, and F. K. LeGoues, "Orientation Dependence of Grain-Boundary Critical Currents in YBa₂Cu₃O_{7-δ} Bicrystals", *Phys. Rev. Lett.*, Vol. 61, 219-222, July 1988.

- [15] L. Fernández, B. Holzapfel, F. Schindler, B. de Boer, A. Attenberger, J. Hänisch, and L. Schultz, "Influence of the grain boundary network on the critical current of $\text{YBa}_2\text{Cu}_3\text{O}_7$ films grown on biaxially textured metallic substrates", *Phys. Rev. B*, vol. 67, 2003, Art. No. 052503.
- [16] X. Obradors and T. Puig, "Coated conductors for power applications: materials challenges", *Supercond. Sci. Technol.*, vol. 27, March 2014, Art. No. 044003.
- [17] Y. Iijima, N. Tanabe, Y. Ikeno, and O. Kohno, "Biaxially aligned $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ thin film tapes", *Physica C*, 185-189, 1959-1960, 1991.
- [18] K. Hasegawa, N. Yoshida, K. Fujinano, H. Mukai, K. Hayashi, K. Sato, T. Ohkuma, S. Honjo, H. Ishii, and T. Hara, "In-plane aligned YBCO thin film tape fabricated by pulsed laser deposition", *Proc. of 16th ICEC / ICMC*, Amsterdam: Elsevier Science, 1413-1416, 1997.
- [19] A. Usoskin, L. Kirchhoff, J. Knoke, B. Prause, A. Rutt, V. Selskij, and D. E. Farrell, "Processing of Long-Length YBCO Coated Conductors Based on Stainless Steel Tapes", *IEEE Trans. Appl. Supercond.*, vol. 17, no. 2, 3235-3238, 2007.
- [20] M. Bauer, R. Semerad, and H. Kinder "YBCO Films on Metal Substrates with Biaxially Aligned MgO Buffer Layers", *IEEE Trans. Appl. Supercond.*, vol. 9, no. 2, 1502-1505, June 1999.
- [21] J. Eickemeyer, D. Selbmann, R. Optiz, E. Maher, and W. Prusseit, "Effect of nickel purity on cube texture formation in RABiT-tapes", *Phys. C Supercond.*, Vvol. 341-348, 2425-2426, Nov. 2000.
- [22] U. Gaitzsch, J. Hänisch, R. Hühne, C. Rodig, J. Freudenberger, B. Holzapfel, and L. Schultz, "Highly alloyed Ni-W substrates for low AC loss applications", *Supercond. Sci. Technol.*, vol. 26, no. 8, July 2013, Art. No. 085024.
- [23] J. Eickemeyer, R. Hühne, A. Güth, C. Rodig, U. Gaitzsch, J. Freudenberger, L. Schultz, and B. Holzapfel, "Textured Ni-9.0% W substrate tapes for YBCO-coated conductors", *Supercond. Sci. Technol.*, vol. 23, no. 8, July 2010, Art. No. 085012.
- [24] R. Hühne, V. Subramanya Sarma, D. Okai, T. Thersleff, L. Schultz, and B. Holzapfel, "Preparation of coated conductor architectures on Ni composite tapes", *Supercond. Sci. Technol.*, vol. 20, no. 7, 709-714, June 2007.
- [25] M. Sieger, J. Hänisch, P. Pahlke, M. Sparing, U. Gaitzsch, K. Iida, R. Nast, E. Reich, L. Schultz, B. Holzapfel, and R. Hühne, "BaHfO₃-doped thick $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ films on highly alloyed textured Ni-W tapes", *IEEE Trans. Appl. Supercond.*, vol. 25, no. 3, 2014, Art. No. 6602604.
- [26] P. Pahlke, M. Lao, M. Eisterer, A. Meledin, G. Van Tendeloo, J. Hänisch, M. Sieger, A. Usoskin, J. Strömer, B. Holzapfel, L. Schultz, and R. Hühne, "Reduced J_c anisotropy and enhanced in-field performance in thick BaHfO₃-doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ films on ABAD-YSZ templates", *IEEE Trans. Appl. Supercond.*, vol. 26, no. 3, March 2016, Art. No. 6603104.
- [27] A. Kiessling, J. Hänisch, T. Thersleff, E. Reich, M. Weigand, R. Hühne, M. Sparing, B. Holzapfel, J. H. Durrell, and L. Schultz, "Nanocolumns in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}/\text{BaZrO}_3$ quasi-multilayers: formation and influence on superconducting properties", *Supercond. Sci. Technol.*, vol. 24, no. 5, March 2011, Art. No. 055018.
- [28] J. Hänisch, C. Cai, V. Stehr, R. Hühne, J. Lyubina, K. Nenkov, G. Fuchs, L. Schultz, and B. Holzapfel, "Formation and pinning properties of growth-controlled nanoscale precipitates in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ /transition metal quasi-multilayers", *Supercond. Sci. Technol.*, vol. 19, no. 6, 534-540, April 2006.
- [29] Tsuruta, Y. Yoshida, Y. Ichino, A. Ichinose, S. Watanabe, T. Horide, K. Matsumoto, and S. Awaji, "Effect of BaHfO₃ introduction on the transport current at the grain boundaries in $\text{SmBa}_2\text{Cu}_3\text{O}_y$ films", *Appl. Phys. Express*, vol. 8, 2015, Art. No. 033101.
- [30] J. L. MacManus-Driscoll, S. R. Foltyn, Q. X. Jia, H. Wang, A. Serquis, L. Civale, B. Maiorov, M. E. Hawley, and D. E. Peterson, "Strongly enhanced current densities in superconducting coated conductors of $\text{YBa}_2\text{Cu}_3\text{O}_{7-x} + \text{BaZrO}_3$ ", *Nat. Mat.*, vol. 3, 439-443, July 2004.
- [31] D. M. Feldmann, T. G. Holesinger, B. Maiorov, S. R. Foltyn, J. Y. Coulter, and I. Apodaca, "Improved flux pinning in $\text{YBa}_2\text{Cu}_3\text{O}_7$ with nanorods of the double perovskite Ba_2YNbO_6 ", *Supercond. Sci. Technol.*, vol. 23, June 2010, Art. No. 095004.
- [32] G. Ercolano, M. Bianchetti, S.-L. Sahonta, A. Kursumovic, J. H. Lee, H. Wang, and J. L. MacManus-Driscoll, "Strong correlated pinning at high growth rates in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ thin films with Ba_2YNbO_6 additions", *Jour. Appl. Phys.*, vol. 116, 2014, Art. No. 033915.
- [33] G. Ercolano, M. Bianchetti, S. C. Wimbush, S. A. Harrington, H. Wang, J. H. Lee, and J. L. MacManus-Driscoll, "State-of-the-art flux pinning in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ by the creation of highly linear, segmented nanorods of $\text{Ba}_2(\text{Y/Gd})(\text{Nb/Ta})\text{O}_6$ together with nanoparticles of $(\text{Y/Gd})_2\text{O}_3$ and $(\text{Y/Gd})\text{Ba}_2\text{Cu}_4\text{O}_8$ ", *Supercond. Sci. Technol.*, vol. 24, August 2011, Art. No. 095012.
- [34] L. Opherden, M. Sieger, P. Pahlke, R. Hühne, L. Schultz, A. Meledin, G. Van Tendeloo, R. Nast, B. Holzapfel, M. Bianchetti, J. L. MacManus-Driscoll, and J. Hänisch, "Large pinning forces and matching effects in $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ thin films with $\text{Ba}_2\text{Y}(\text{Nb/Ta})\text{O}_6$ nano-precipitates", *Scientific Reports*, vol. 6, 2016, Art. No. 21188.
- [35] M. Sieger, P. Pahlke, J. Hänisch, M. Sparing, M. Bianchetti, J. MacManus-Driscoll, M. Lao, M. Eisterer, A. Meledin, G. Van Tendeloo, R. Nast, L. Schultz, B. Holzapfel, and R. Hühne, " $\text{Ba}_2\text{Y}(\text{Nb/Ta})\text{O}_6$ doped YBCO films on biaxially textured Ni-5at.% W substrates", *IEEE Trans. Appl. Supercond.*, vol. 26, no. 3, 2016, Art. No. 7500305.
- [36] F. Rizzo, A. Augieri, A. Angrisani Armenio, V. Galluzzi, A. Mancini, V. Pinto, A. Rufoloni, A. Vannozzi, M. Bianchetti, A. Kursumovic, J. L. MacManus-Driscoll, A. Meledin, G. Van Tendeloo, and G. Celentano, "Enhanced 77 K vortex-pinning in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ films with Ba_2YTaO_6 and mixed $\text{Ba}_2\text{YTaO}_6 + \text{Ba}_2\text{YNbO}_6$ nano-columnar inclusions with irreversibility field to 11 T", *APL Mater.*, vol. 4, 2016, Art. No. 061101.
- [37] P. Pahlke, M. Hering, M. Sieger, M. Lao, M. Eisterer, A. Usoskin, J. Strömer, B. Holzapfel, L. Schultz, and R. Hühne, "Thick high J_c YBCO films on ABAD-YSZ templates", *IEEE Trans. Appl. Supercond.*, vol. 25, no. 3, 2015, Art. No. 6603804.
- [38] W. Prusseit, R. Nemetschek, C. Hoffmann, G. Sigl, A. Lümekemann and H. Kinder, "ISD process development for coated conductors", *Phys. C Supercond.*, vol. 426-431, 866-871, 2005.
- [39] F. Hengstberger, M. Eisterer, M. Zehetmayer, and H. W. Weber, "Assessing the spatial and field dependence of the critical current density in YBCO bulk superconductors by scanning Hall probes", *Supercond. Sci. Technol.*, vol. 22, Jan. 2009, Art. No. 025011.
- [40] B. Maiorov, S. A. Baily, H. Zhou, O. Ugurlu, J. A. Kennison, P. C. Dowden, T. G. Holesinger, S. R. Foltyn, and L. Civale, "Synergetic combination of different types of defect to optimize pinning landscape using BaZrO₃-doped $\text{YBa}_2\text{Cu}_3\text{O}_7$ ", *Nat. Mat.*, vol. 8, 398-404, 2009.
- [41] F. Baca, P. N. Barnes, R. L. S. Emergo, T. J. Haugan, J. N. Reichart, and J. Z. Wu, "Control of BaZrO₃ nanorod alignment in $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ thin films by microstructural modulation", *App. Phys. Lett.*, vol. 94, March 2009, Art. No. 102512.
- [42] P. Pahlke, M. Sieger, P. Chekhonin, W. Skrotzki, J. Hänisch, A. Usoskin, J. Strömer, L. Schultz, and R. Hühne, "Local orientation variations in YBCO films on technical substrates - a combined SEM and EBSD study", *IEEE Trans. Appl. Supercond.*, vol. 26, no. 3, Apr. 2016, Art. No. 7201505.
- [43] M. Sieger, P. Pahlke, R. Ottolinger, B. Stafford, M. Lao, A. Meledin, M. Bauer, M. Eisterer, G. Van Tendeloo, L. Schultz, K. Nielsch and, R. Hühne, "Influence of vicinal substrates on the incorporation of BaHfO₃ in thick $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ films", *IEEE Trans. Appl. Supercond.*, accepted for publication (DOI: 10.1109/TASC.2016.2631587).
- [44] E. Reich, T. Thersleff, R. Hühne, K. Iida, L. Schultz, and B. Holzapfel, "Structural and pinning properties of $\text{Y}_2\text{Ba}_4\text{CuMO}_y$ ($M = \text{Nb}, \text{Zr}$)/ $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ quasi-multilayers fabricated by off-axis pulsed laser deposition", *Supercond. Sci. Technol.*, vol. 22, Aug. 2009, Art. No. 105004.
- [45] F. J. Baca, R. L. Emergo, J. Z. Wu, T. J. Haugan, J. N. Reichart, and P. N. Barnes, "Microstructural Characterization of $\text{YBa}_2\text{Cu}_3\text{O}_{7-x}$ Films With BaZrO₃ Nanorods Grown on Vicinal SrTiO₃ Substrates", *IEEE Trans. Appl. Supercond.*, vol. 19, no. 3, 3371-3374, 2009.
- [46] M. Lao, J. Hecher, M. Sieger, P. Pahlke, M. Bauer, R. Hühne, and M. Eisterer, "Planar current anisotropy and field dependence of J_c in coated conductors assessed by scanning Hall probe microscopy", *Supercond. Sc. Tech.*, accepted for publication (SUST-101801), 2017.